



E-ISSN: 2709-9385
P-ISSN: 2709-9377
JCRFS 2023; 4(2): 39-44
© 2023 JCRFS
www.foodresearchjournal.com
Received: 10-05-2023
Accepted: 22-06-2023

S Rahul

College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

K Nikshitha

College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

S Keerthana

College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

M Bhavani

College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

Samreen

Assistant Professor, College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

R Swamy

Associate Dean, College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

Correspondence

S Keerthana

College of Food Science and Technology, Rudrur, PJTS Agricultural University, Telangana State, India

Development of biodegradable cups from pomegranate peel powder

S Rahul, K Nikshitha, S Keerthana, M Bhavani, Samreen and R Swamy

Abstract

Plastics are mixture of organic polymers that play a major role in environmental contamination worldwide. The demand for plastic containers was increasing over the past few decades. One way to reduce the waste arising from the use of plastics, especially disposable ones, can be to produce environmental friendly biodegradable materials. Biodegradable cutlery is an upcoming line fruit waste utensils that are totally safe to be used and boon for eco-system. An attempt was made to prepare biodegradable cups using pomegranate peel powder. Glycerol was added as plasticizer. Whereas, xanthan gum used as binding agent. The study was conducted to find out the standard cup made with different ratios of raw materials in each treatment. Quality analysis such as tensile strength, bursting strength, water leakage test and biodegradability test were studied for different treatments like T₁ with 50:25:25, T₂ with 70:15:15 and T₃ with 90:05:05.

Keywords: Biodegradable cups, pomegranate, peel powder

Introduction

The result revealed higher tensile strength for the T₂ than T₁ and T₃. It was observed that higher glycerol content the lower will be the tensile strength. But the cup made with glycerol content of 15% which is in T₂ was observed to be strong. Increasing the xanthan gum also increases the bursting strength of cups. Highest bursting strength observed for T₁ i.e., 5.18 kg/cm². Increased amount of glycerol increase the permeability of water in the cups. So, the T₂ cup resist more water than T₁ and T₃. Biodegradability test reported that the cup made with T₂ degrades faster than T₁ and T₃. Cups made with pomegranate waste have good biodegradability than the plastic cups.

Materials and Methods

This chapter deals with raw materials used, experimental methodology and measurement techniques adopted during the course of investigation. The systematic approach adopted for preparation of biodegradable cups with natural colors was presented. The study was carried out in the College of Food Science and Technology, Rudrur.

Procurement of raw materials

Pomegranate peel powder was extracted from the peels collected. Xanthan gum, glycerol and food colours were purchased from local market. Glassware and moulds were used for moulding of cups.

Extraction of peel powder from pomegranates

Pomegranates were collected from the local market. The collected pomegranate fruits were washed with water and cleaned. The cleaned pomegranates were peeled and dried by using a hot air oven at a temperature of 104 °C for 5 h. Then the dried pomegranate peels were ground into fine powder. Fine powder was obtained by sieving.

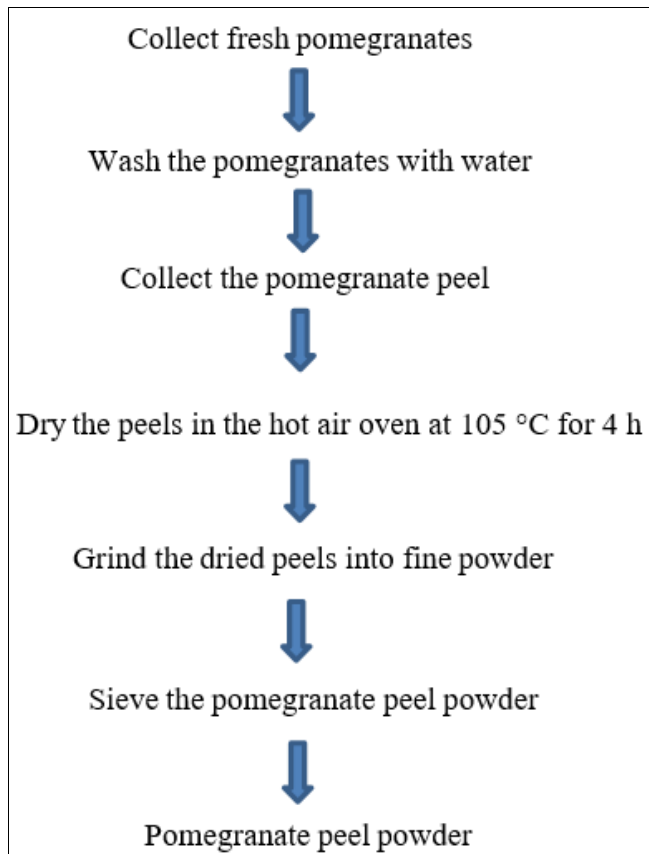


Fig 1: Flow chart for extraction of pomegranate peel powder

After extraction of pomegranate peel powder, xanthan gum and glycerol were added in different proportions. The different proportions for the preparation of biodegradable cups with addition of xanthan gum and glycerol were shown in Table 1

Table 1: Different proportions for preparation of biodegradable cups

Treatments	Proportions		
	Pomegranate peel powder	Xanthan gum	Glycerol
T ₁	50	25	25
T ₂	70	15	15
T ₃	90	5	5

Preparation of biodegradable cups

The preparation of dough samples was made by addition of water to the composite mixture of pomegranate peel powder, xanthan gum, glycerol. The prepared dough was placed in moulds for moulding to form cups. Care was taken to get uniform thickness throughout the cup. Food colours were also incorporated in the dough to prepare different coloured cups. After moulding process, the mould with dough were placed in tray dryer at 75 °C for 8 h for drying. After drying remove the cup from the mould. The time-temperature combination was decided based on preliminary trails. The different steps involved in preparation of biodegradable cups.

Preparation of Bio Degradable Cups

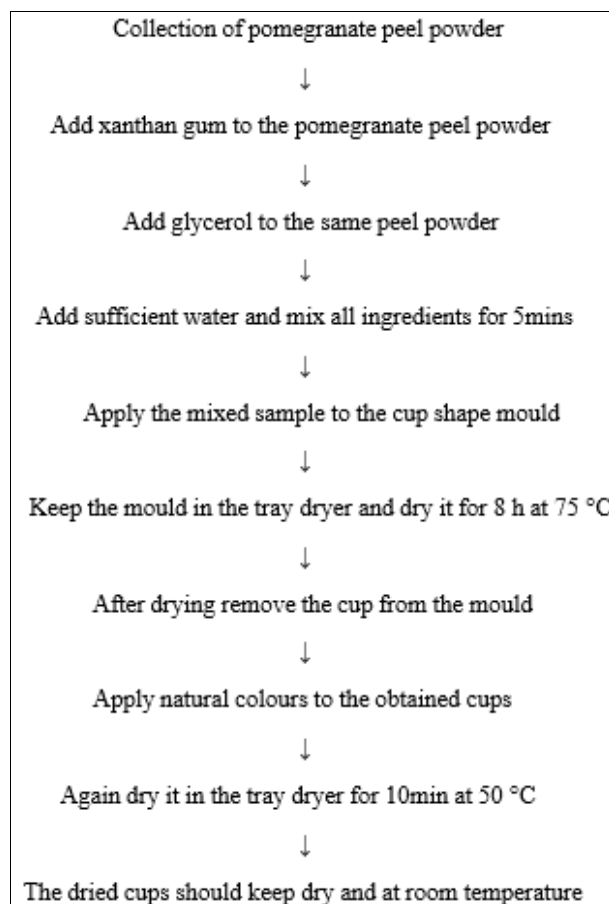


Fig 2: Flow chart for preparation of biodegradable cups from pomegranate peel powder

Quality Analysis

The quality analysis was conducted to the prepared biodegradable cups by using pomegranate peel powder and finding the standard cup among the cups made with different proportions of pomegranate peel powder, xanthan gum and glycerol.

Tensile Strength Test

The tensile strength of biodegradable cups was determined according to the procedure given by Buxoo *et al.*, (2020) [5] by using a tensile strength tester. The tensile strength test indicates the ability of the cup sample to resist a rupture force applied parallel to it. Grammage of the prepared cups was calculated by rolling to have uniform thickness. Then grammage value was entered at calibration board in the tester. Then pressing the start button on the screen to show the final reading of tensile strength values for the treatments made with different proportions.

Calculation

$$\text{Tensile strength (nominal), kg/cm}^2 = \frac{\text{Max. load}}{\text{Original min. Cross sectional area of specimen}}$$

Tensile strength (at break), kg/cm² = max. Load at break/ original min. Cross sectional area of specimen

Breaking factor (nominal), kg/cm² = max. Load/original thickness of specimen

Bursting Strength Tester

The bursting strength of biodegradable cups was determined according to Buxoo *et al.*, (2020) [5] by using the bursting strength tester. The bursting strength tester works based on the principle that the maximum hydrostatic pressure required to produce a rupture of the material when controlled and constantly increasing pressure is applied through a rubber diaphragm. The prepared dough sample sheet was kept under the bursting strength tester by entering the grammage value calculated. Then enter the start button on screen were showed the final obtained bursting strength values of prepared proportion. The higher the bursting strength the stronger will be the material.

Calculation

Bursting strength (kg/cm^2) = Burst factor* GSM (GM/m^2)/ 1000

Burst factor = bursting strength (Gm/m^2)/ grammage (gm/m^2)

Biodegradability in soil

Biodegradation was tested in soil under controlled laboratory conditions (25 °C, Relative humidity 25% and pH=7). The film samples were placed in plastic container filled with soil. Biodegradation was analysed by taking photographs regularly.

Results and Discussion

In this chapter, the results obtained for the biodegradable cups prepared by using pomegranate peel powder were presented. Quality analysis of biodegradable cups was evaluated and discussed.

Tensile Strength

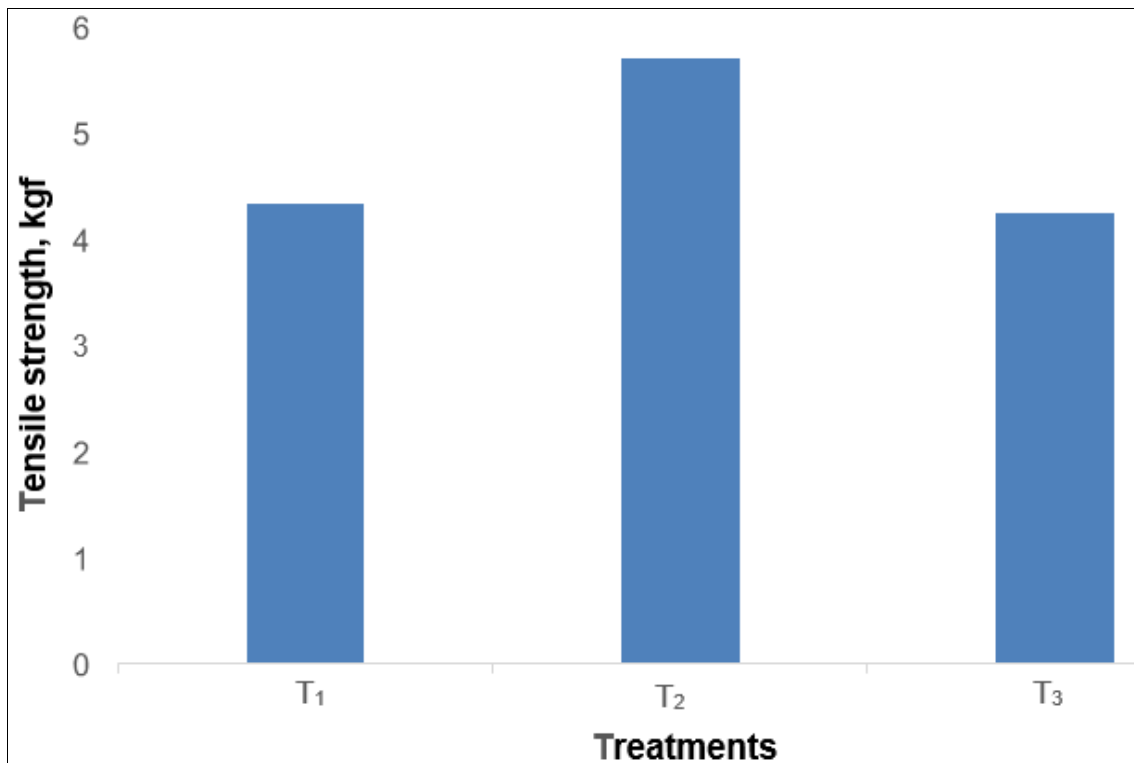


Fig 3: Changes of tensile strength of biodegradable cups prepared with pomegranate peel powder

Tensile strength was evaluated for the biodegradable cups made with pomegranate peel powder with addition of xanthan gum and glycerol. The results were shown in Fig 4.1. It was observed that the treatment, T₂ recorded higher values of tensile strength of 5.7 kgf. The other two treatments T₁ and T₃ recorded 4.33 kgf and 4.25 kgf, respectively.

Similar trend was observed by Pawinee *et al.* (2019) when biodegradable film were prepared with incorporation of cassava starch. It was observed that increase in glycerol content decreased the tensile strength. Whereas, the lower amount of glycerol produced the brittle films, while the increased glycerol content resulted in sticky films.

Another trend was observed by Jiang *et al.* (2015) [13] when paper based plastics were prepared with incorporation of glycerol and chloride solution. It was observed that increase

in glycerol content decrease the tensile strength.

Another trend was observed by Hidayati *et al.* (2021) [9] when biodegradable film was prepared by seaweed waste with incorporation of glycerol and carboxy methyl cellulose. It was observed that increase in glycerol content decrease the tensile strength whereas increased amount of carboxy methyl cellulose increase the tensile strength.

Bursting strength

Bursting strength was evaluated for the biodegradable cups made with pomegranate peel powder with addition of xanthan gum and glycerol. The results were shown in Fig 4.2. It was observed that the treatment, T₁ recorded higher values of bursting strength of 5.18 kg/cm^2 . The other two treatments T₂ and T₃ recorded 5.02 kg/cm^2 and 4.37 kg/cm^2 , respectively.

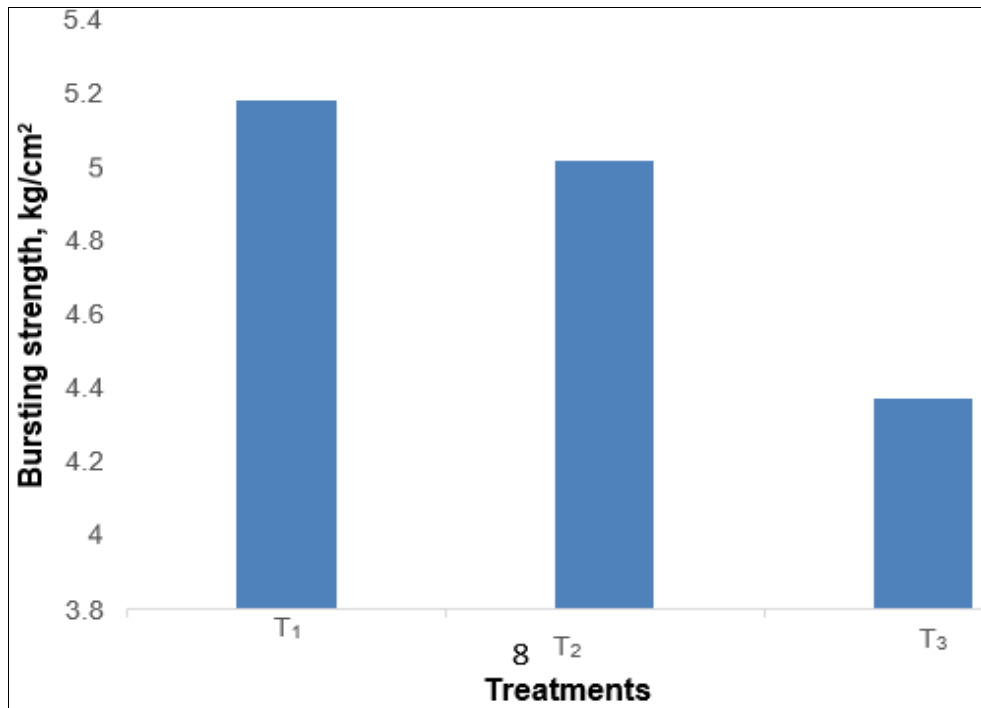


Fig 4: Changes of bursting strength of biodegradable cups prepared with pomegranate peel powder

Similar trend was observed by Jiang *et al.* (2015) [13] when paper based plastics were prepared with incorporation of glycerol and chloride solution. It was observed that without addition of glycerol and low glycerol content leads to low bursting strength.

the biodegradable cups made with pomegranate peel powder with addition of xanthan gum and glycerol. The results were shown in Fig. 4.3. It was observed that the Treatment, T₂ took more time to leak water i.e. 4 h when compared to treatments, T₁ and T₃ i.e., 3 h and 2 h, respectively.

Water leakage Test: Water leakage test was evaluated for

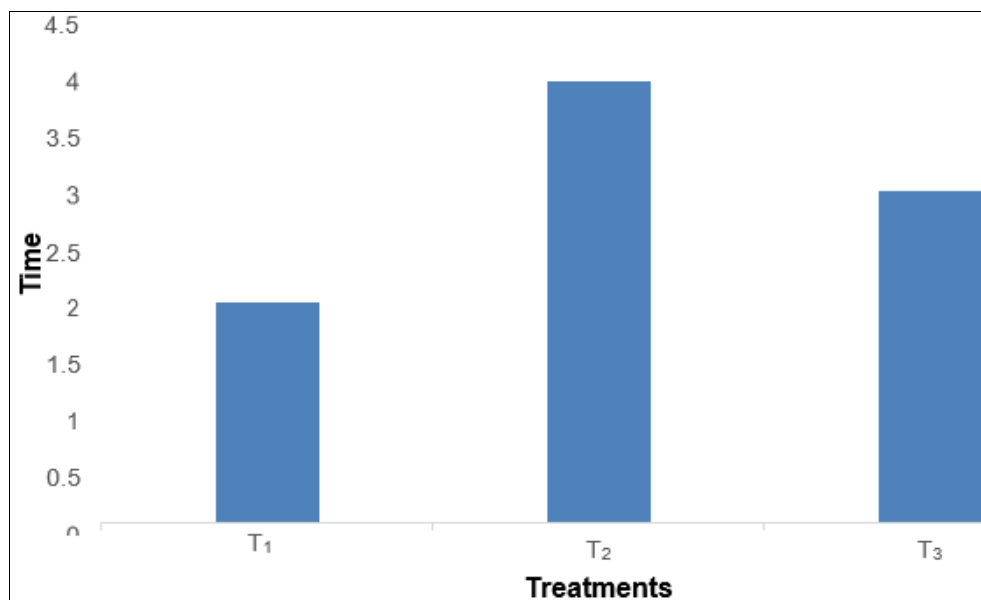


Fig 5: Changes in water leakage test of biodegradable cups prepared with pomegranate peel powder

Similar trend was observed by Pawinee Theamdee *et al.* (2019) when films prepared with cassava starch with incorporation of glycerol. It was observed that with increasing in glycerol concentration the water vapour permeability increased. Also films with increasing glycerol exhibit hydrophilic character.

sample of 5 g from each different compositions in the soil at room temperature. The biodegradable cups prepared with different proportions of pomegranate peel powder, xanthan gum and glycerol were degraded completely after 1 month. Each sample was gradually disintegrated and started decaying within 4 to 5 days. The complete decay was observed within 1 month. The process of degradation of the cups prepared is due to the bacteria in the soil and organic substances present in it.

Biodegradability Test

The biodegradability test was performed by placing a

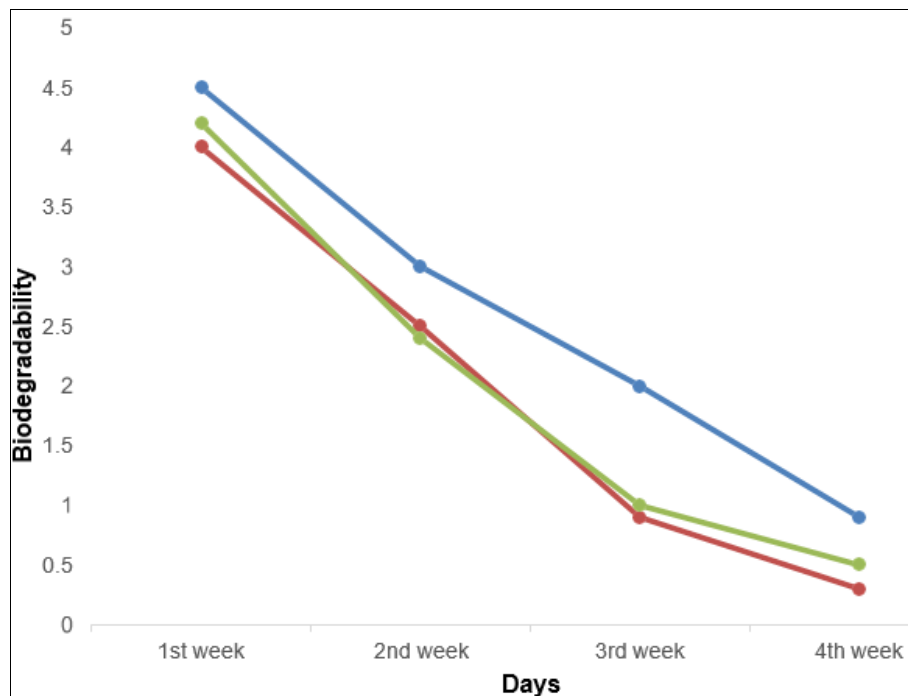


Fig 6: Changes in biodegradability of biodegradable cups prepared with pomegranate peel powder

Conclusions

The present study entitled with “Development of biodegradable cups with pomegranate peel powder” was carried out in college of Food Science and Technology, Rudrur. The study was conducted with the objectives to develop biodegradable cups made from pomegranate peels as an alternative to plastic cups and to reduce the fruit waste obtained from fruit processing industries.

Plastic waste disposal is a major cause of environmental pollution. Disposal of single use plastic has a tremendous impact on the surrounding environment. As an alternative to plastics, biodegradable cups were developed from pomegranate waste mostly from peels which are eco-friendly and biodegradable.

The biodegradable cups were developed by using pomegranate peel powder, Xanthan gum and Glycerol. Xanthan gum is an additive used as a binding agent also the glycerol used as binder and plasticizer. These samples were taken in different proportions to develop the standard cup which resist the water from leakage and not to react with the food material we use. T₁ having ppp, xanthan gum and glycerol in the ratio 50:25:25. Were T₂ in the ratio 70:15:15 and finally the T₃ in the ratio 90:5:5. were mixing ppp, xanthan gum & glycerol well together with sufficient water to make dough so that it should ready to mould. Then applying it to the cup mould shape and drying it in tray dryer for 8 h at 75 °C. After drying the cup was coated with natural food colour and stored at cool and dry place.

References

- Gadallah M, Shabib Z, El-Hazmi T. Development of High Dietary Fibre- Enriched Cupcake Using Pomegranate Peel Powder. *International Journal of Food Science*, 2022; c2022.
- Dr. Saini AK. Groundwater pollution, its causes, and enhancement by surface water pollution and prevention techniques. *Int. J Adv. Chem. Res.* 2022;4(2):346-350. DOI: 10.33545/26646781.2022.v4.i2e.132
- Acquavia MA, Pascale R, Martelli G, Bondoni M, Bianco G. Natural polymeric materials: A solution to plastic pollution from the agro-food sector. *Polymers.* 2021;13(1):158.
- Lacivita V, Incoronato AL, Conte A, Del Nobile MA. Pomegranate peel powder as a food preservative in fruit salad: A sustainable approach. *Foods.* 2021;10(6):1359.
- Buxoo S, Jeetah P. Feasibility of producing biodegradable disposable paper cup from pineapple peels, orange peels and Mauritian hemp leaves with beeswax coating. *SN Applied Sciences.* 2020;2:1-15.
- Chen J, Liao C, Ouyang X, Kahramanoğlu I, Gan Y, Li, M, *et al.* Antimicrobial activity of pomegranate peel and its applications on food preservation. *Journal of Food Quality*; c2020. p. 1-8.
- Khan S, Patel A, Bhise KS. Antioxidant activity of pomegranate peel powder. *Journal of Drug Delivery and Therapeutics.* 2017;7(2):81-84.
- Yaradoddi J, Patil V, Ganachari S, Banapurmath N, Hunashyal A, Shettar A, *et al.* Biodegradable plastic production from fruit waste material and its sustainable use for green applications. *Int. J Pharm. Res. Allied Sci.* 2016;5(4):72-81.
- Hidayati S, Maulidia U, Satyajaya W, Hadi S. Effect of glycerol concentration and carboxy methyl cellulose on biodegradable film characteristics of seaweed waste. *Heliyon.* 2021;7(8):e07799.
- Beevi KR, Fathima AS, Fathima AT, Thameemunisa N, Noorjahan CM, Deepika T, *et al.* Bioplastic synthesis using banana peels and potato starch and characterization. *International journal of scientific & technology research.* 2020;9(1):1809-1814.
- Gustafsson J, Landberg M, Bátor V, Åkesson D, Taherzadeh MJ, Zamani A, *et al.* Development of bio-based films and 3D objects from apple pomace. *Polymers.* 2019;11(2):289.
- Pansaeng N. The Effect of glycerol on the properties of biodegradable cassava starch (Saai Dieow Cultivar) films for plastic plant bag application. *Naresuan University Journal: Science and Technology (NUJST).*

- 2019;27(4):27-38.
13. Jiang X, Han J, Han Q, Zhou X, Ma J. Preparation and characteristics of paper-based biodegradable plastics. *Bio Resources*. 2015;10(2):2982-2994.
 14. Meenambal T, Uma RN, Saravannan S. Study on biodegradation of fruit waste aerobic composting. Department of Geography, University of Madras and Faculty of Environmental Studies, York University; c2003. p. 441-450.
 15. Vyshali P, Serena PB. Development of an edible and biodegradable tableware using fruit wastes-an alternative to plastic tableware. *Int. J Food Nutr. Sci*. 2022;11:85-90.